

Hunter Douglas Europe BV  
Piekstraat 2  
3071 EL Rotterdam  
NETHERLANDS

**Eurofins Product Testing A/S**  
Smedeskovvej 38  
8464 Galten  
Denmark

[voc@eurofins.com](mailto:voc@eurofins.com)  
[www.eurofins.com/voc-testing](http://www.eurofins.com/voc-testing)

Date  
26 August 2015


# VOC Emission Test report

## 1. Sample Information

Sample identification	Hunter Douglas Felt Linear
Product type	Ceiling panel
Batch no.	V4560/3+002/00
Production date	15 May 2015
Date when sample was received	13/07/2015
Testing (start - end)	22/07/2015 - 19/08/2015

## 2. Resulting VOC Emission Class Label

This recommendation is based on French regulation of March 23, 2011 (décret DEVL1101903D) and of April 19, 2011 (arrêté DEVL1104875A). For details please see [www.eurofins.com/france-voc](http://www.eurofins.com/france-voc)

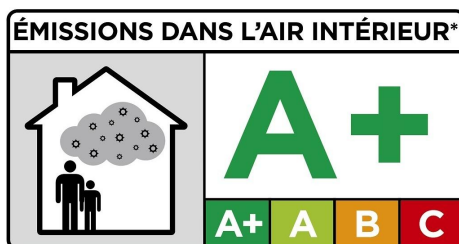

\*Information sur le niveau d'émission de substances volatiles dans l'air intérieur, présentant un risque de toxicité par inhalation, sur une échelle de classe allant de A+ (très faibles émissions) à C (fortes émissions).

The product was assigned a VOC emission class without taking into account the measurement uncertainty associated with the result. As specified in French Decree no. 2011-321 of March 23, 2011, correct assignment of the VOC emission class is the sole responsibility of the party responsible for distribution of the product in the French market.

## 3. Conclusion on CMR emissions

The tested product fulfills the requirements of the French regulation DEVP0908633A of 30 April 2009 and DEVP0910046A of 28 May 2009. For details please see [www.eurofins.com/france-voc](http://www.eurofins.com/france-voc).

The results are only valid for the tested sample(s).

This report may only be copied or reprinted in its entirety, parts of it only with a written acceptance by Eurofins.

#### 4. Test Method

Method	Principle	Parameter	Quantification limit	Uncertainty	
ISO 16000 parts -3, -6, -9, -11 Internal method numbers: 9810, 9811, 9812, 2808B, 8400	GC/MS HPLC/UV	VOC Volatile aldehydes	2 µg/m <sup>3</sup> 3 µg/m <sup>3</sup>	22% (RSD)	
ISO 16000 parts -3, -6, -9, -11 Internal method numbers: 9810, 9811, 9812, 2808B, 8400, 2616	GC/MS	4CMR	<1 µg/m <sup>3</sup>	Um = 2 x RSD=45 %	
<b>Test chamber parameter</b>					
Chamber volume, l	119	Temperature, °C	23±1	Relative humidity, %	50±3
Air change rate, 1/h	0.5	Loading ratio, m <sup>2</sup> /m <sup>3</sup>	1.4 *		
<b>Test condition: Sample stayed in test chamber during the whole 28 days testing period.</b>					
<b>Sample preparation</b>					
The sample was transferred directly into the chamber.					

\* The results have been recalculated to a loading factor of 0.4m<sup>2</sup>/m<sup>3</sup>.

## 5. Results

	Concentration after 28 days $\mu\text{g}/\text{m}^3$	C	B	A	A+
TVOC	< 2	>2000	<2000	<1500	<1000
Formaldehyde	< 3	>120	<120	<60	<10
Acetaldehyde	< 3	>400	<400	<300	<200
Toluene	< 2	>600	<600	<450	<300
Tetrachloroethylene	< 2	>500	<500	<350	<250
Ethylbenzene	< 2	>1500	<1500	<1000	<750
Xylene	< 2	>400	<400	<300	<200
Styrene	< 2	>500	<500	<350	<250
2-Butoxyethanol	< 2	>2000	<2000	<1500	<1000
1,2,4-Trimethylbenzene	< 2	>2000	<2000	<1500	<1000
1,4-Dichlorobenzene	< 2	>120	<120	<90	<60
<b>CMR compounds</b>		Maximum allowed air concentration			
Benzene	< 1	<1			
Trichloroethylene	< 1	<1			
Dibutylphthalate (DBP)*	< 1	<1			
Diethylhexylphthalate (DEHP) *	< 1	<1			

< Means less than

> Means higher than

\* Not a part of our accreditation (EN ISO/IEC 17025:2005) by DANAK (no. 522))



Thomas Bjerring  
Analytical Service Manager



Maria Pelle  
Chemist

The results are only valid for the tested sample(s).

This report may only be copied or reprinted in its entity, parts of it only with a written acceptance by Eurofins.